



Received on 18 July, 2017; received in revised form, 21 April, 2018; accepted, 24 April, 2018; published 01 May, 2018

FORMULATION AND EVALUATION OF FLURBIPROFEN OCULAR *IN-SITU* GEL

Sravan Kumar Aligeti*, Raj Kumar Jampala and J. Vinaya

Vaageswari College of Pharmacy, (Affiliated to JNTUH, Hyderabad), Karimnagar - 505481, Telangana, India.

Keywords:

In-situ gelling systems, Flurbiprofen, Carbopol 934, Carbopol 940, Carbopol 971 and HPMC E15, HPMC K4M, and HPMC K100, pH sensitive systems, Ocular delivery

Correspondence to Author:

Sravan Kumar Aligeti

Associate Professor,
Vaageswari College of
Pharmacy, Beside LMD Police
Station, Ramakrishna Colony,
Karimnagar - 505401,
Telangana, India.


E-mail: sravan.aligeti@gmail.com

ABSTRACT: Conventional ophthalmic preparations exhibit poor bioavailability due to the rapid precorneal elimination of the drug, and the physiological constraints imposed by the protective mechanisms of the eye lead to the low absorption of the drugs resulting in a short duration of the therapeutic effect. In order to increase the residence time of the drug *in-situ* gelling systems were prepared and instilled as drops into the eye which undergo a sol-gel transition in the cul-de-sac. The present work describes the formulation and evaluation of flurbiprofen ocular *in-situ* gel, based on the concept of pH - triggered *in-situ* gelation. Polyacrylic acid (carbopol) was used as the gelling agent in combination with hydroxy-propyl methyl cellulose (HPMC) which acted as a viscosity enhancing agent. The formulations were evaluated for clarity, pH measurement, gelling capacity, gelling temperature, drug content estimation, rheological study, *in-vitro* drug release study, sterility testing and stability studies. The physicochemical interactions between drug and polymers were investigated by fourier transform infrared (FTIR) spectroscopy. FTIR studies did not show any evidence of interaction between the drug and the polymers. The formulation F22 (containing 1% HPMC E15, 0.3% carbopol 971) showed sustained release over a period of 8 h follows, first order mechanism.

INTRODUCTION: Topical application of drugs to the eye is the well established route of administration for the treatment of various eye diseases like dryness, conjunctiva, inflammation, eye flu *etc.* The protective mechanisms of the eye such as blinking, baseline and reflex lachrymation, and drainage decrease the bioavailability of drug and also help to remove rapidly foreign substances like the dust particles, including drugs, from the surface of the eye¹.

Topically applied drugs do not reach the posterior segment of the eye (retina, vitreous, choroid); therefore systemic administration, per ocular or intraocular injections of drugs are normally applied in clinical therapeutics². The unique anatomy and physiology of the eye and its protective barriers prevent the administered drugs from protecting into the target tissues.

There are many eye diseases which can affect the eye and also eye vision. Therefore marketed ophthalmic formulations are classified as conventional and non-conventional (novel) drug delivery systems³. There are most commonly available ophthalmic preparations such as drops and ointments which render 70% of the eye dosage formulations in the market.

QUICK RESPONSE CODE 	DOI: 10.13040/IJPSR.0975-8232.9(5).1851-56
	Article can be accessed online on: www.ijpsr.com
DOI link: http://dx.doi.org/10.13040/IJPSR.0975-8232.9(5).1851-56	

But these preparations when installed into the eye are rapidly drained away from the ocular surface due to blinking tear flow and lachrymal nasal drainage of the eye. Only a small amount of the drug is available for its therapeutic effect resulting in need for frequent application to the eye⁴. So to overcome these problems novel pharmaceutical ophthalmic formulations such as *in-situ* gel, nanoparticle^{5, 6} liposome, nano suspension^{7, 8}, micro emulsion⁹, inophoresis and ocular inserts have been developed in last three decades to increase the bioavailability of the drug in a sustained and controlled manner.

Conventional ocular drug delivery systems like eye drops require frequent instillations to maintain a therapeutic drug level at the site of action, whereas, gels have difficulty in instillation into the eye. An alternative approach has been the application of *in-situ* gelling systems which are instilled in a liquid form and shift to a gel form in the cul-de-sac^{11, 12}. The phase transition is triggered by the pH of the tears, the temperature at the eye surface or the electrolytes present in the tear film. Ophthalmic use of non-steroidal anti-inflammatory drugs (NSAIDs) offers several benefits after intraocular and refractive surgery¹³. NSAIDs also can reduce patients' intra- and postoperative pain; help maintain pupillary dilation,

control inflammation after surgery. Flurbiprofen is a non-steroidal anti-inflammatory drug used to treat eye infections such as corneal ulcers, seasonal allergic conjunctivitis and reduce inflammation following cataract surgery.

MATERIALS AND METHODS: Flurbiprofen, carbopol (934, 940 and 971), HPMC (E15, K4M, K100) and ethanol.

Preparation of *in-situ* Gels of Flurbiprofen: Aqueous solutions of varying concentrations of different polymers and drug were prepared and evaluated for gelling capacity and viscosity in order to identify the compositions suitable for use as *in situ* gelling systems.

All ingredients were weighed accurately and the formulations were prepared by dispersing different grades of polymers carbopol (934, 940 and 971) solutions in different concentrations (0.1% w/v, 0.3% w/v, and 0.5% w/v) and HPMC (E15, K4M and K100) solutions in different concentrations (1% w/v and 1.5% w/v) in distilled water with continuous stirring until completely dispersed and allowed to hydrate overnight. Flurbiprofen (0.03%) was dissolved in 0.5 ml of ethanol and then added to the above polymeric solutions under constant stirring to obtain a uniform solution.

TABLE 1: COMPOSITION OF *IN-SITU* GELLING SYSTEMS BY pH SENSITIVE SYSTEMS

Formulation code	Drug (%w/v)	Carbopol 934 (% w/v)	Carbopol 940 (% w/v)	Carbopol 971 (% w/v)	HPMC E15 (% w/v)	HPMC K4M (% w/v)	HPMC K100 (% w/v)	Benzalkonium chloride (% w/v)	Distilled water (% w/v)
F1	0.03	0.1	-	-	-	-	-	0.02	qs
F2	0.03	0.3	-	-	-	-	-	0.02	qs
F3	0.03	0.5	-	-	-	-	-	0.02	qs
F4	0.03	-	0.3	-	-	-	-	0.02	qs
F5	0.03	-	0.5	-	-	-	-	0.02	qs
F6	0.03	-	-	0.3	-	-	-	0.02	qs
F7	0.03	-	-	0.5	-	-	-	0.02	qs
F8	0.03	-	-	-	1	-	-	0.02	qs
F9	0.03	-	-	-	1.5	-	-	0.02	qs
F10	0.03	-	-	-	-	1	-	0.02	qs
F11	0.03	-	-	-	-	1.5	-	0.02	qs
F12	0.03	-	-	-	-	-	1	0.02	qs
F13	0.03	-	-	-	-	-	1.5	0.02	qs
F14	0.03	0.3	-	-	1	-	-	0.02	qs
F15	0.03	-	0.3	-	-	1	-	0.02	qs
F16	0.03	-	-	0.3	-	-	1	0.02	qs
F17	0.03	-	0.3	-	-	-	1	0.02	qs
F18	0.03	-	-	0.3	-	1	-	0.02	qs
F19	0.03	0.3	-	-	-	1	-	0.02	qs
F20	0.03	0.3	-	-	-	-	1	0.02	qs
F21	0.03	-	0.3	-	1	-	-	0.02	qs
F22	0.03	-	-	0.3	1	-	-	0.02	qs

*qs to 100 ml

The pH of the solution was adjusted to 7.4 using 0.1N NaOH solution. Benzalkonium chloride (BKC) was then added to the above solution and mixing was confirmed until uniform and clear obtained. Final volume was made up by adding required amount of distilled water. All the formulations were terminally sterilized by autoclaving at 121 °C and 15 lb for 15 min.

Evaluation of Ocular *in-situ* Gels:

Clarity: The clarity of the formulations before and after gelling was determined by visual examination of the formulations under light alternatively against white and black backgrounds.

pH: The developed ophthalmic formulations were evaluated for pH using digital pH meter. Ophthalmic formulations should have a pH range in between 4.0 - 7.4.

Drug Content: Ocular *in-situ* gel of flurbiprofen was assayed by spectrophotometric analysis. The formulation (1 ml) was taken in a 100 ml volumetric flask diluted with simulated tear fluid (STF) pH 7.4 and was shaken to dissolve the drug in STF pH 7.4. The solution was filtered through Whatman filter paper; this filtrate was further diluted if necessary with PBS pH 7.4. Drug content was determined using a shimadzu UV 1800 double beam spectrophotometer at 247 nm.⁵

Measurement of Gelling Capacity: The prepared *in-situ* gelling system was evaluated for gelling capacity in order to identify the composition suitable for use as *in-situ* gelling systems. The *in-situ* gelling system was mixed with simulated tear fluid (in the proportion of 25:7 which means the application volume of 25 µl and normal volume of

tear fluid in the eye is 7 µl) to find out the gelling capacity of the ophthalmic product. The gelation was then visually assessed by noting the time for gelation and time taken for the gel formed to dissolve.

TABLE 2: EVALUATION OF CLARITY, pH, DRUG CONTENT AND GELLING CAPACITY OF ALL FORMULATIONS

Formulation code	Clarity	pH	Drug content	Gelling capacity
F1	Clear	7.2	98.3±1.1	+
F2	Clear	7.0	99.7±1.2	+
F3	Clear	7.3	101.3±0.9	++
F4	Clear	7.0	97.9±1.3	++
F5	Clear	7.0	99.9±1.1	++
F6	Clear	7.1	99.3±0.9	++
F7	Clear	7.2	99.5±0.5	+++
F8	Clear	7.0	98.5±0.6	++
F9	Clear	7.1	99.1±0.1	++
F10	Clear	6.9	98.7±1.1	+
F11	Clear	6.7	99.1±0.3	+

TABLE 3: EVALUATION OF CLARITY, pH, DRUG CONTENT AND GELLING CAPACITY OF ALL FORMULATIONS

Formulation code	Clarity	pH	Drug content	Gelling capacity
F12	Cloudy	6.5	102.3±0.2	S
F13	Cloudy	6.6	98.7±0.6	S
F14	Clear	7.3	98.7±1.1	++
F15	Clear	7.1	98.5±0.7	++
F16	Cloudy	6.8	96.5±0.5	S
F17	Cloudy	6.7	97.5±1.1	S
F18	Clear	7.0	99.1±1.3	+
F19	Clear	7.1	98.4±1.3	+
F20	Cloudy	6.9	99.5±1.0	S
F21	Clear	7.2	99.6±1.0	+
F22	Clear	7.4	99.5±0.5	+++

*Mean ± SD, n = 3, “+”: gels after a few minutes, dissolves rapidly; “++”: gelation immediate, remains for few hours; “+++”: gelation immediate, remains for extended period; “s”: gelation immediate, remains for extended period but gels are stiff

TABLE 4: EVALUATION OF VISCOSITY OF ALL FORMULATIONS

Formulation code	Viscosity (cp) at 20 rpm		Formulation code	Viscosity (cp) at 20 rpm	
	Before gelation (25 °C)	After gelation (37 °C)		Before gelation (25 °C)	After gelation (37 °C)
F1	117	980	F12	912	2166
F2	192	1128	F13	989	2331
F3	675	2005	F14	698	1433
F4	586	2341	F15	735	1554
F5	600	1468	F16	1003	2443
F6	656	1669	F17	1243	2256
F7	768	1985	F18	512	1992
F8	832	1764	F19	326	1008
F9	884	2052	F20	1126	2892
F10	497	1296	F21	776	2257
F11	634	1945			

Rheological Studies: Rheological studies were conducted using a Brookfield synchroelectric viscometer (LVDV Pro II). The developed formulation was poured into the small sample adaptor of the brookfield synchroelectric viscometer¹¹ and the viscosity was measured at non-physiological (pH 4 and 25 °C) and physiological condition (pH 7.4 and 37 °C) respectively.

TABLE 5: VISCOSITIES OF OPTIMIZED *IN-SITU* GEL FORMULATIONS AT DIFFERENT RPM

RPM	F22	
	Viscosity (cp)	
	Before gelation (25 °C)	After gelation (37 °C)
10	300	1026
20	274	980
30	215	880
50	192	653
100	145	540

***In-vitro* Diffusion Studies:** *In-vitro* drug release study of the formulation was carried out by diffusion process. It was performed on Franz diffusion cell using semi permeable membrane was soaked overnight in the receptor medium (STF, pH 7.4) and tied to one end of the glass diffusion cell.

TABLE 6: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F1 TO F4

Time-h	F1	F2	F3	F4
1	3.20±1.150	9.61±2.423	14.5±2.995	18.9±1.885
2	4.81±2.000	13.9±2.905	18.2±3.756	27.1±4.108
3	7.11±2.189	18.4±3.196	25.1±1.015	32.5±3.392
4	10.8±2.469	23.2±3.007	30.6±2.027	37.2±3.407
5	14.3±2.852	28.2±4.467	35.6±2.955	42.6±4.107
6	18.9±3.569	32.1±3.049	41.6±3.307	48.8±4.657
7	23.2±4.400	34.4±3.881	46.5±3.968	54.2±3.510
8	28.2±4.914	36.8±4.883	51.9±4.086	60.0±2.885

TABLE 7: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F5 TO F8

Time-h	F5	F6	F7	F8
1	31.0±2.516	26.5±1.607	36.8±0.642	23.2±0.916
2	42.6±1.882	29.4±1.587	42.2±2.005	30.5±1.527
3	50.6±3.000	34.8±1.677	44.9±3.066	31.9±1.050
4	54.4±2.008	44.5±1.607	51.1±2.150	36.8±1.527
5	57.3±1.401	50.0±2.081	57.3±1.686	42.4±2.523
6	63.9±0.550	52.3±3.027	62.6±2.884	46.5±4.700
7	67.3±1.527	56.7±2.502	67.4±3.094	51.3±3.482
8	69.7±2.400	62.4±3.055	70.9±2.951	60.1±2.950

TABLE 8: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F9 TO F12

Time-h	F9	F10	F11	F12
1	8.10±1.185	12.5±1.054	8.10±2.042	11.2±1.442
2	11.2±1.845	18.6±2.950	11.4±2.081	16.6±3.353
3	13.5±1.755	25.1±1.648	17.7±2.451	25.1±2.478
4	18.4±1.379	33.5±1.250	23.8±1.594	36±2.605
5	24.8±1.267	40.6±2.100	32.3±2.370	46.8±3.686
6	29.8±3.511	48.4±2.708	36.6±3.931	52.3±4.005
7	34.4±2.500	56.2±4.574	45.7±1.824	57.7±2.930
8	44.5±4.273	68.9±1.606	50.7±2.605	65.8±2.461

The donar compartment was filled with 1 ml formulation and the receptor compartment was filled with 25 ml of simulated tear fluid, assuring that the membrane was just touched the receptor surface. The whole assembly was adjusted on a magnetic stirrer and the temperature was maintained at 34 ± 0.5 °C. Aliquots were diluted with the stimulated tear fluid and analyzed by UV-visible spectrophotometer at 247 nm.

TABLE 9: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F13 TO F16

Time-h	F13	F14	F15	F16
1	10.0±1.958	5.80±1.539	10.3±2.225	7.70±1.692
2	16.6±2.802	12.5±1.654	16.2±5.040	16.6±4.080
3	24.7±3.254	17.8±4.088	28.6±3.358	29.6±3.840
4	28.2±3.561	28.6±2.753	36.9±3.111	37.5±4.349
5	32.5±4.181	36.9±3.922	45.7±2.897	47.0±2.884
6	37.7±3.892	46.5±3.288	54.2±3.401	53.4±2.326
7	45.1±4.443	53.8±4.440	68.4±0.949	61.6±3.709
8	53.4±3.357	67.4±3.635	72.8±1.038	65.0±2.599

TABLE 10: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F17 TO F21

Time-h	F17	F18	F19	F20	F21
1	8.43	12.5	10.4	7.30	11.2
	±2.851	±3.151	±3.511	±0.862	±1.442
2	14.8	18.9	16.2	14.3	15.5
	±4.132	±4.279	±3.991	±1.950	±2.753
3	21.3	26.7	28.6	22.4	24.8
	±2.321	±4.955	±3.597	±2.951	±4.233
4	25	33.3	35.4	27.5	29.8
	±3.908	±4.755	±4.009	±2.876	±2.882
5	32.5	43.6	41.6	34.1	36.6
	±3.774	±5.118	±4.392	±4.324	±3.941
6	35.6	51.1	47.6	42.6	44.3
	±5.641	±4.352	±5.296	±3.222	±3.959
7	45.7	61.6	57.7	50.9	60.3
	±4.654	±3.154	±3.745	±2.615	±4.639
8	51.5	67.8	64.3	60.4	63.9
	±4.669	±3.514	±4.720	±2.142	±4.824

Optimised Formula:

TABLE 11: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F22

Time-h	% Drug release
0	0±0.00
1	16.2±1.15
2	30.5±2.67
3	55.6±3.87
4	60.5±3.57
5	69.7±2.98
6	76.6±4.34
7	80.5±3.85
8	86.7±4.97

Sterility Studies:

TABLE 12: TEST OF STERILITY

Formulation code	Days of incubation						
	1	2	3	4	5	6	7
T5	-	-	-	-	-	-	-
P8	-	-	-	-	-	-	-

Where “ - ” sign indicate no growth

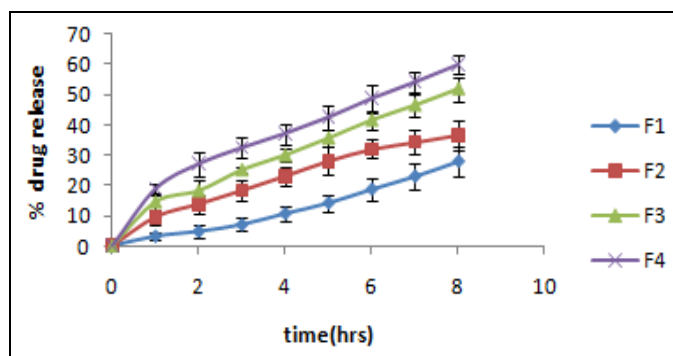


FIG. 1: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F1 TO F4

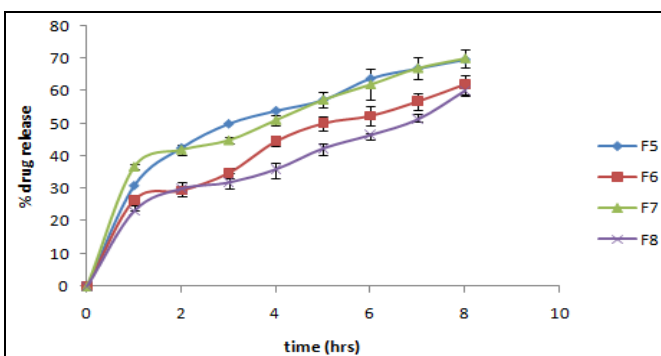


FIG. 2: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F5 TO F8

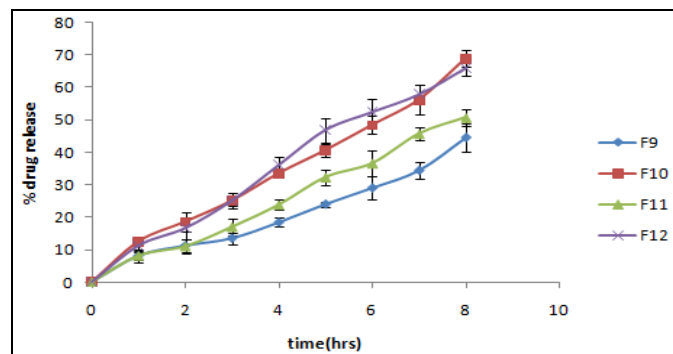


FIG. 3: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F9 TO F12

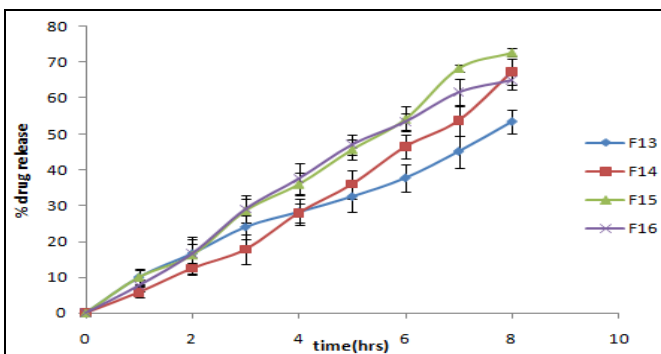


FIG. 4: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F13 TO F16

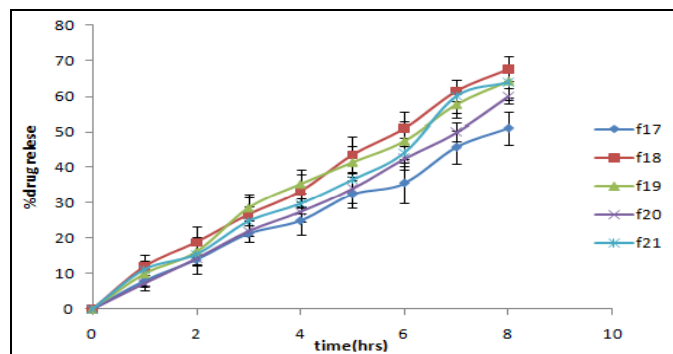


FIG. 5: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F17 TO F21

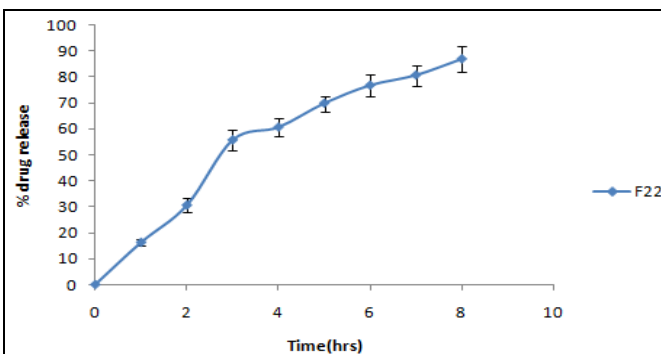


FIG. 6: *IN-VITRO* DRUG RELEASE PROFILE OF FORMULATION F22

The optimised formulation F22 were evaluated for the sterility. After 7 days of incubation the results showed no microbial growth in the formulation.

CONCLUSION: In this study, ophthalmic in situ gelling system of flurbiprofen was successfully formulated with polymers carbopol 934, carbopol 940, carbopol 971 and HPMC E15, HPMC K4M, HPMC K100 for pH- triggered *in-situ* gelling system. Flurbiprofen, is a non-steroidal anti-inflammatory agent used in the treatment of ocular inflammations. Optimized formulation F22, flurbiprofen (0.03% w/v %) using carbopol 971 (0.3% w/v %) as a gelling agent in combination with HPMC E15 (1% w/v) as a viscosity enhancing agent.

The formulation underwent gelation in the cul-de-sac upon instillation as drops into the eyes. The formulation was found to be clear, having good in situ gelling capacity. Optimized formulation was sterile and showed sustained drug release over 8 h period. The formulation showed sustained drug release with prolonged drug residence time, thereby increasing the effectiveness of the drug by localization at the site of action.

ACKNOWLEDGEMENT: The first author is thankful to G. Srinivas Reddy chairman, Vaageswari Educational Society, Karimnagar, Telangana, India for providing infrastructure and research facilities.

CONFLICT OF INTEREST: The author reports no conflicts of interest.

REFERENCES:

1. Kaur H, Loyee S and Garg R: Formulation and evaluation of *in-situ* ocular gel of gatifloxacin, Int J Pharma Res Health Sci. 2016; 4(5): 1365-1370.
2. Shaikh A, Farheen T and Shahi S: Formulation development and evaluation of pH triggered in situ ophthalmic gel of epinastine hydrochloride. IJPSR 2016; 7(3): 1131-1138.
3. Patil SK, Kadam A, Bandgar S and Patil SK: Formulation and evaluation of an *in-situ* gel for ocular drug delivery of anticonjunctival drug. Cellulose Chem. Technol. 2015; 49(1): 35-40.
4. Dol H, Gandhi S, Pardhi D and Vyawahare N: Formulation and evaluation of *in-situ* ophthalmic gel of moxifloxacin hydrochloride, The Pharma Innovation Journal 2014; 3(5): 60-6.
5. Makwana SB and Patel VA: Development and characterization of *in situ* gel for ophthalmic formulation containing ciprofloxacin hydrochloride. Results in Pharma Sciences 2015; 6: 1-6.
6. Shaikh et al.: Formulation development and evaluation of pH triggered *in-situ* ophthalmic gel of epinastine hydrochloride. IJPSR 2016; 7(3): 1131-1138.
7. Kaur H et al.: Formulation and evaluation of *in-situ* ocular gel of gatifloxacin. IJPRHS 2016; 4(5): 1365-1370.
8. Shahi and Deshpande: Iontophoresis: An approach to drug delivery enhancement, IJPSR 2017; 8(10): 4056-4068.
9. Dasankoppa FS et al.: Design, formulation, and evaluation of *in-situ* gelling ophthalmic drug delivery system comprising anionic nonionic polymers 2017;10(3):323-30.
10. Paradkar MU et al.: formulation development and evaluation of natamycin niosomal *in-situ* gel for ophthalmic drug delivery, Journal of Drug Delivery Science and Technology 2017; 39: 113e122.
11. Balasingam R et al.: Formulation of *in-situ* gelling system for ophthalmic delivery of erythromycin. International Journal of Students' Research in Technology and Management 2017; 5(3): 01-08.
12. Kotreka UK: Development of topical ophthalmic *in-situ* gelforming estradiol delivery system intended for the prevention of age-related cataracts PLOS ONE / journal. pone.0172306, 2017.
13. Saini R: *In-situ* gels - a new trends in ophthalmic drug delivery systems. International Journal of Pharma Sciences and Research (Ijpsr) 2015; 6(5): 886-890.

How to cite this article:

Aligeti SK, Jampala RK and Vinaya J: Formulation and evaluation of flurbiprofen ocular *in-situ* gel. Int J Pharm Sci Res 2018; 9(5): 1851-56. doi: 10.13040/IJPSR.0975-8232.9(5).1851-56.

All © 2013 are reserved by International Journal of Pharmaceutical Sciences and Research. This Journal licensed under a Creative Commons Attribution-NonCommercial-ShareAlike 3.0 Unported License.

This article can be downloaded to **ANDROID OS** based mobile. Scan QR Code using Code/Bar Scanner from your mobile. (Scanners are available on Google Playstore)