



Received on 27 July, 2016; received in revised form, 04 October, 2016; accepted, 07 October, 2016; published 01 February, 2017

DEVELOPMENT OF PRINTING NATURAL FABRICS WITH CURCUMA NATURAL DYE VIA NANOTECHNOLOGY

A. A. Ragheb¹, S. Tawfik², J. I. Abd –El Thalouth² and M. M. Mosaad^{*2}

Textile Research Division¹, National Research Centre, Cairo, Egypt.

Faculty of Applied arts², Helwan University, Cairo, Egypt.

Keywords:

Textile, Printing,
Nanotechnology, Natural dye,
Curcuma dye, Natural fabrics

Correspondence to Author:

J.I.Abd –El Thalouth

Faculty of Applied arts, Helwan University, Textiles printing, dyeing and finishing department, Cairo, Egypt.

E-mail: jackyibm@yahoo.com

ABSTRACT: The present work is undertaken with a view to harness nanotechnology as one of the most important frontier sciences for development of printing natural fabrics using the most eco-friendly dyes, i.e. natural colors. Curcuma natural dye was studied to clarify the impact of nature of nano-size color particles on size, shape, and particle distribution of the natural dye with comparative studies of the K/S and over all fastness properties of printed samples on natural fabrics (wool, silk and cotton). Results showed that the K/S values of nano samples are higher than original samples, irrespective of the nature of the fabric used and /or the concentration of the coloring matter. Alum mordant incorporated with original curcuma can be omitted, and substituted by nano-curcuma without mordant. K/S values of the pre-mordanting acquired the higher values than the simultaneous mordanting irrespective of the fabric used, or dye particles size used, or curcuma concentrations on using tannic acid mordant. Color fastness to rubbing, and perspiration properties of nano dye is better than the original.

INTRODUCTION: Natural dyes are as old as textiles themselves¹. They have been used by humans for purposes varying from coloration of food, cosmetics and textiles to imparting other functions to them². *Curcuma longa* L., which known as turmeric was used as a coloring matter and also as medical properties³ belongs to the Zingiberaceae family, originates from the Indian subcontinent and possibly neighboring areas of Southeast Asia, but it is nowadays widely grown throughout the tropics.

Its tuberous rhizomes used as a condiment, a colorant and an aromatic stimulant since antiquity. The pigments in the colorant extracts obtained from Curcuma collectively known as curcuminoids, the major constituent being curcumin, along with small amounts of demethoxycurcumin and bisdemethoxycurcumin **Fig. 1**^{4,5}.

| | |
|-----------------------------------|---|
| <p>QUICK RESPONSE CODE</p> | <p>DOI: 10.13040/IJPSR.0975-8232.8(2).611-20</p> <hr/> <p>Article can be accessed online on: www.ijpsr.com</p> <hr/> <p>DOI link: http://dx.doi.org/10.13040/IJPSR.0975-8232.8(2).611-20</p> |
|-----------------------------------|---|

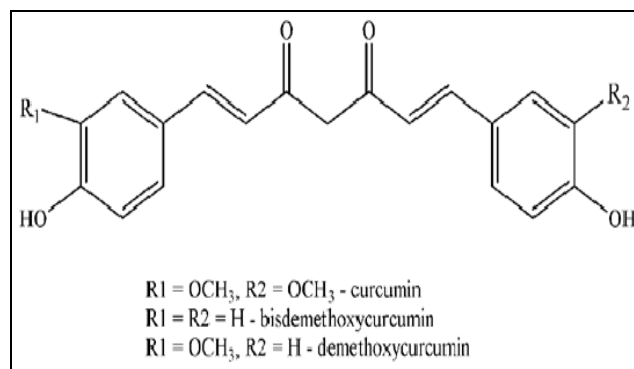


FIG. 1: STRUCTURE OF CURCUMIN AND ITS ANALOGS.

Curcumin and other related curcuminoids are reported to be responsible for yellow color of the dye⁶. Ghoreishian and coworkers dyed silk fabric with turmeric and proved antibacterial properties to silk fabric⁷.

The coloring is due to curcuma in which is insoluble in water but soluble in organic solvents such as acetone, ethanol and hexane. A product produced by extracting turmeric with organic solvent and essential oil) from which curcumin (the yellow dye) can be produced by evaporating the essential oil. Turmeric (curcumine) is used as a vegetable dye to give a rich yellow color to silk, cotton and wool. Curcumin has anti-inflammatory, antifungal and antitumorous. It is also widely used as food colorant. It is called C.I Natural Yellow 3, its color index number is C.I, 75300, E100⁸.

Several shortcomings are encountered with conventional natural coloration, of these are poor wet rubbing fastness, light fastness, poor shades and harsh hand resulting from regular size dye particles and nature of the binder used⁹.

To overcome these problems, improving the dispersion of the natural dye becomes necessary. Modification of natural dye morphology can decrease the average of dye particle's diameter to 100-200 nm and, in so doing; the natural dye dispersion acquires greater stability and color strength approaching that of dyes¹⁰.

The urgent need for innovative technology, as alternative for the conventional production process, for achieving lower cost, cleaner production process and products, as well as attaining improved lifetime, better quality and performance properties is actually a global necessity. Nanotechnology occupies a top position among frontier technologies that responds to this need¹¹.

Nanotechnology first started as an idea in a 1959 conference talk with Richard Feynman¹². Nanotechnology is the science and technology of designing, constructing and creating of novel nano-scale structure, 1nm to 100 nm in size, with huger quality, novel performance properties, along with fewer defects compared with those of the bulk material¹³.

It can provide high durability to fabrics, because nanoparticles have a large surface area-to-volume ratio and high surface energy, thus presenting better affinity for fabrics and leading to an increase in durability of the function¹⁴.

When a matter is reduced in size, it changes its characteristics, such as color and interaction with other matter i.e., chemical activity. The change in characteristics is caused by the change of the electronic properties. By particle size reduction, the surface area of the material is increased. Due to this, a higher percentage of atoms can interact with other matter.

Nanoparticles must be closely regulated so that their properties are not altered¹⁵.

The present work is undertaken with a view to harness nano-technology as one of the most important frontier sciences for development of printing natural fabrics using the most eco-friendly dyes namely curcuma. This was done to clarify the import of nature of nano-size color particles on size, shape and particles distribution of the natural dyes with comparative studies of the K/S and overall fastness properties. Role of miniaturization of the used curcuma on its printability of cotton, wool and silk in presence and absence of mordants will be investigated.

2. EXPERIMENTAL:

2.1. Materials:

Fabrics:

- Cotton fabrics: Mill desized, bleached and mercerized cotton fabrics 165 g/m² produced by Misr/Helwan for Spinning and Weaving Company, Helwan, Egypt.
- Wool fabrics: Mill scoured 100% wool fabrics 210g/m², supplied by Misr Company for spinning and weaving (Mehalla El-Kubra), Mehalla, Egypt.
- Silk fabrics: Mill scoured natural Silk fabric of plain weave 60 g/m² supplied by El-Khateib Company, Souhag, Upper Egypt.

Dyestuff: Natural Coloring substance turmeric (Curcuma) [which have been purchased from local market] was extracted according to the procedure described latter.

Thickening agents: Commercial synthetic thickening agent, namely Printofixthickener MTB 01 EG liq manufactured by Clariant Company was also used.

Mordants: Alum [hydrated double sulfate of potassium hydrogen sulfate ($KAl(SO_4)_2 \cdot 12H_2O$), and tannic Acid ($C_76H_{52}O_{46}$).

2.2 METHODS:

2.2.1. Extracting of natural coloring matter: 100 g Curcuma dry powder were added to 1000 ml. water and subjected to boiling under reflux for 30 min. The mixture was left to cool at room temperature and then filtrated off. The filtrated solution was concentrated using a laboratory Rotavapour.

2.2.2. Preparation of nano particles of curcuma natural dye using Ultrasonic stirrer: Different amount "X" (3, 5, or 7gm) of filtrated solution of Curcuma were suspended in 100ml distilled water under stirring then the solution were set to motion in the Ultrasonic stirrer (The probe is turned to resonate at specific frequency, 20 KHZ \pm 100 HZ). The Ultrasonic stirrer was operated for 60 min at ca 80°C to reach the nano-size.

2.2.3. Preparation of the printing pastes: The extracted curcuma color was subjected to minimization using Ultrasonic stirrer as previously mentioned. Different printing pastes containing natural curcuma color before and after minimization were prepared according to the following recipes:

| | |
|--|-------|
| Dye suspension original or nano sample * | 20 g |
| Urea | 2.5 g |
| Thickener | 2.5 g |
| Binder | 5 g |
| Sodium dihydrogen phosphate dehydrate | 0.5 g |
| Mordant ** | X |
| Distilled water | Y |
| Total | 100 |

* 20g was taken from each dyeing solution (original or nano-size) containing curcuma color at a concentration of 3, 5, or 7 g dye in 100 ml water.

** The mordant was incorporated direct in the printing paste.

2.2.4. Mordanting of natural fabrics: Mordanting of the natural fabrics (cotton, wool or silk) were conducted using two different techniques; either pre-mordanting or simultaneous i.e. added directly to the printing were used.

2.2.5. Printing techniques: The aforementioned three different fabrics, i.e. cotton, wool, or silk were printed with the prepared printing paste via screen, i.e. screen printing technique. After printing and dyeing the printed goods were subjected to steaming at 115°C for 10 minutes for silk, and for 20 minutes for both cotton and wool followed by thoroughly washing and finally air-dried. At the end, the fabrics were assessed for K/S and overall fastness properties.

2.3. Testing, Analysis and measurements:

2.3.1. Transmission electronic micro-scropy (TEM) ¹⁶: Particle shape and Size were obtained using a JEOLJEM 1200. Specimens for TEM measurements were prepared by dissolving a drop of colloid solution on a 400 mesh copper grid coated by an amorphous carbon film and evaporating the solvent in air at room temperature. The average diameter of the natural dye nanoparticles was determined from the diameter of 100 nanoparticles found in several arbitrarily chosen areas in enlarged microphotographs.

2.3.2. Color strength and fastness: The color strength (K/S) of the samples was evaluated by light reflectance technique using Shimadzu UV/Visible spectrophotometer ¹⁷, and the overall color fastness properties: i.e. to washing, perspiration or rubbing fastness were assessed according to standard methods ¹⁸.

3. RESULTS AND DISCUSSION:

3.1. Dependence of the size of curcuma particles on its concentration: To start with TEM investigation of the particles size of the curcuma color, **Fig. 2, 3 and 4** show the TEM micrographs of curcuma at original size, i.e. before subjecting to ultrasonic stirring at a concentration of 3, 5 and 7%. **Fig. 5, 6 and 7** represents the particle size after subjecting to ultrasonic stirring for 60 min, at Ca 80°C.

A close examination of **Fig.2** which represent the TEM at a concentration of a concentration of 3% before subjecting to ultrasonic stirring signifies as average particle size of 223nm. Indeed this average covers a wide distribution of size particles ranging from 159.4 to 291.7 nm. While **Fig. 5** represents TEM micrograph of the same sample after subjecting to ultrasonic technique. **Fig. 3, 4** and

Fig. 6, 7 represent the TEM before and after miniaturization at concentrations of 5 and 7 % respectively.

While **Table 1** summarize the effect of concentration of curcuma on the particle size before and after nanofication.

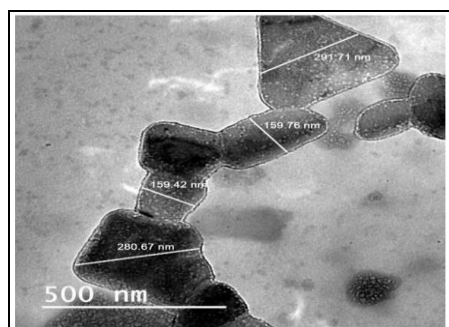


FIG. 2: 3% ORIGINAL CURCUMA

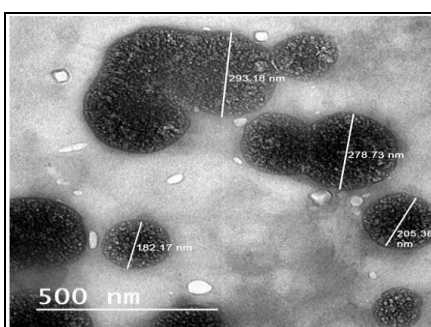


FIG. 3: 5% ORIGINAL CURCUMA

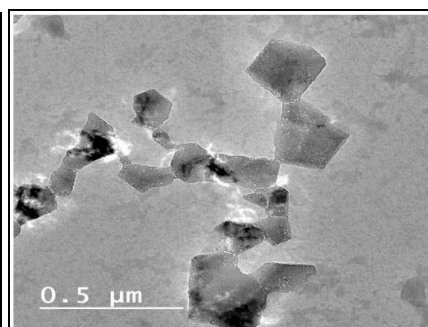


FIG.4: 7% ORIGINAL CURCUMA

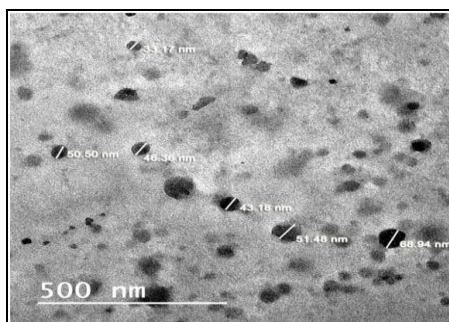


FIG.5: 3% NANO CURCUMA

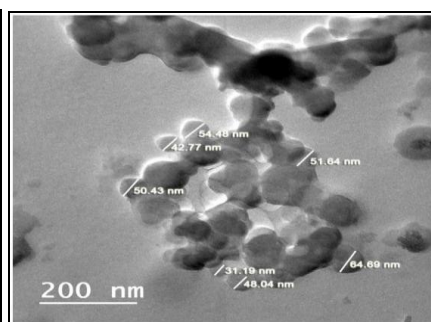


FIG.6: 5% NANO CURCUMA

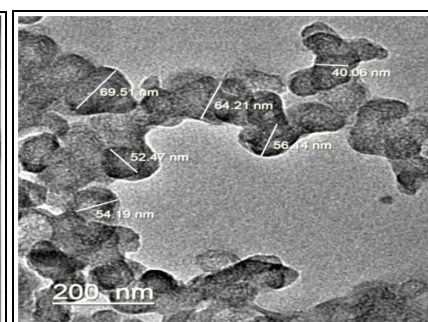


FIG. 7: 7% NANO CURCUMA

TABLE 1: COMPARISON BETWEEN CURCUMA PARTICLE SIZE BEFORE AND AFTER MINIATURIZATION USING ULTRASOUND BASED TECHNIQUE

| Dye | Con. of dye | Original size | | | Nano size | | | Percent decrease |
|---------|-------------|------------------------------|---------------------------|---------------------------|------------------------------|---------------------------|---------------------------|------------------|
| | | Average size of dye particle | Max. size of dye particle | Min. size of dye particle | Average size of dye particle | Max. size of dye particle | Min. size of dye particle | |
| Curcuma | 3% | 222.9 | 291.7 | 159.4 | 43.7 | 68.9 | 33.2 | 80.39% |
| | 5% | 239.9 | 293.2 | 182.2 | 49.1 | 64.7 | 31.2 | 79.53% |
| | 7% | 261.5 | 419.5 | 176.3 | 56.1 | 69.5 | 40.1 | 78.55% |

It is clear from the micrographs that the size, shape and particle size distribution of nano-dye rely on dye concentration. It was found that at lower concentration, the nanoparticles exhibit a perfectly uniform spherical shape with broad particle size distribution and with little or no evidence of aggregation / agglomeration. The above finding and those connected with changes in shape and particle size distribution could be explained in terms of disintegration of the dye to much smaller size of large surface areas, which favor the possibility of aggregation and agglomeration. It is clear from the data that, by increasing the

concentration of the curcuma dye from 3-7%, the average size of the nano-dye particle increased, in both original size and nano-size. The decrease percentage of miniaturization of particle size are (80.39 %, 79.53%, 78.55%) at dye concentrations of (3, 5, and 7%) respectively. This reflects the higher effectiveness of ultrasonic stirrer in severely breaking down the dye particles through the growth of cavitation.

3.2. Effect of miniaturization of curcuma color to nano-sized on its printability on natural fabrics: To investigate the effect of decreasing the

particle size of curcuma to the nano-form on its printability on natural fabrics, printing pastes containing the aforementioned three concentrations before and after miniaturization were prepared in presence or absence of mordants.

3.2.1. Comparison between original and nano-size: (In absence of mordant): Table 2 represents the data of K/S obtained using different concentrations of curcuma before and after miniaturization.

TABLE 2: EFFECT OF MINIATURIZATION OF CURCUMA COLOR TO NANO-SIZED ON K/S IN ABSENCE OF MORDANT.

| Fabric | Dye Con. % | K/S Without mordant | | |
|-----------|------------|---------------------|--------------|-------------------|
| | | In original form | In nano Form | % increase in K/S |
| On Wool | 3 | 1.49 | 2.47 | 65.8% |
| | 5 | 2.18 | 2.72 | 24.8% |
| | 7 | 2.24 | 2.75 | 22.8% |
| On Silk | 3 | 1.31 | 2.53 | 93.1% |
| | 5 | 2.06 | 2.73 | 32.5% |
| | 7 | 2.17 | 2.21 | 1.8% |
| On Cotton | 3 | 0.51 | 1.73 | 239.2% |
| | 5 | 1.50 | 3.34 | 122.7% |
| | 7 | 1.48 | 1.81 | 22.3% |

It is clear from the data of **Table 2** that the K/S is oppositely related to the size of the nano particles. Decreasing the particle size is accompanied by substantial enhancement in color strength.

The increase in K/S on decreasing the particle size to the nano-scale may be due to the virtue of their small nano-scale size and large surface area which make the particle diffuse faster in the interior of the printed fabrics and distributed themselves on the fabric surface during printing. In so doing, they produce prints with strong color shade and, therefore, higher color strength compared with the original particles which acquire relatively larger size.

It is clear from the data, Irrespective of the fabric used, the K/S values of nano samples are higher than original samples.

Proteic fabrics i.e. wool and silk acquire high affinity for natural colors than cellulosic fiber i.e. cotton. It has been reported¹⁹ that natural dyes are high molecular weight compounds containing phenolic hydroxyl groups which enable them to form effective cross-links between proteins such as wool and silk, where they form three types of bonds namely. (a) Hydrogen bond: which is formed between phenolic hydroxyl groups of natural dye and the free amino and amides groups of the proteins. (b) Ionic bond: it is formed between suitable charged anionic groups of the natural dye and cationic groups on the protein. (c) Covalent bond: it is formed by interaction of any quinone or

semi quinone group present in natural dye with any suitable reactive groups in the protein.

However in case of cellulosic, exemplified by cotton, the natural dye could form only two types of bonds as follows: (a) Hydrogen bond: which is formed between phenolic hydroxyl groups of natural dye and the hydroxyl groups of cellulose. (b) Covalent bond which may be formed by the interaction of quinone or semi quinone groups present in natural dye with suitable functional groups in the cellulose.

In addition, as the concentration of the curcuma dye increases, the K/S value increases irrespective of the particle size.

3.2.2. Comparison between original and nano-size of curcuma dye in presence of pre-mordant: Irrespective of the fabric used; the K/S values of nano samples are higher than original samples. This phenomenon holds true in order to a matter is reduced in size, it changes its characteristics, such as color and interaction with other matter.

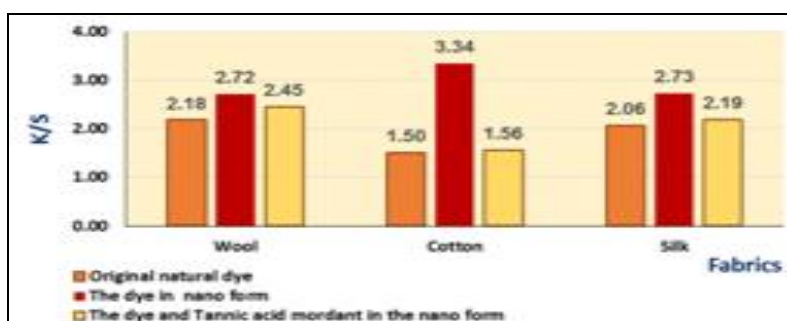
3.2.3. Comparison between nano-dye and original dye with mordant: To investigate the possibility of using nano-dye instead of using mordants with original dye. Different samples (wool, silk or cotton) were printed with different mordants (alum or Tannic acid) incorporated with original curcuma dye, while other samples printed with only nano-curcuma dye for comparison.

TABLE 3: COMPARISON BETWEEN PRINTING DYE IN NANO-FORM, AND DYE IN ORIGINAL FORM INCORPORATE WITH MORDANT

| Nature of fabric | Dye conc. % | K/S of Nano dye | K/S of original dye incorporate with mordant | |
|------------------|-------------|-----------------|--|-------------|
| | | | Alum | Tannic acid |
| Wool | 3% | 1.49 | 1.32 | 2.09 |
| | 5% | 2.18 | 1.71 | 2.39 |
| | 7% | 2.24 | 2.40 | 2.28 |
| Silk | 3% | 2.53 | 1.20 | 2.27 |
| | 5% | 2.73 | 1.45 | 2.71 |
| | 7% | 2.21 | 1.94 | 3.17 |
| Cotton | 3% | 1.73 | 0.62 | 1.43 |
| | 5% | 3.34 | 0.95 | 2.15 |
| | 7% | 1.81 | 1.66 | 2.23 |

It is clear from the data of **Table 3** that; the K/S values of nano-dye samples are higher than the original dye incorporate with alum mordant when applied at cotton or silk fabric. Therefore, alum mordant incorporate with original curcuma can be substituted by nano-curcuma without mordant.

3.2.4. Comparison between original-dye, nano-dye, and nano-dye incorporated with nano-Tannic acid at dye concentration 5%: It is clear from **Fig. 8** that, the dye in nano form acquired the highest K/S values compared with original-dye, and incorporate dye and tannic acid in the nano form at dye concentration 5%.

**FIG. 8: COMPARISON BETWEEN K/S OF CURCUMA DYE IN ORIGINAL AND NANO- SIZE AND NANO-DYE INCORPORATE WITH NANO-TANNIC ACID**

3.2.5. Effect of mordanting technique on K/S of printing curcuma colorant in original form: To study techniques of mordanting (pre-mordanting and simultaneous mordanting) of Alum/Tannic acid mordants and their effects on printing curcuma in original form, on wool, silk or cotton samples, and compared with non-mordanted samples, The K/S values were remarked as shown in **Table 4**.

On using Alum mordant: The highest K/S values was obtained on using 7% of curcuma dye, irrespective of the fabric used or the applied technique. On using Tannic mordant: the K/S of pre-mordant samples is higher than the simultaneous samples irrespective of fabric used.

3.2.6. Comparison between using pre-mordanting and simultaneous mordanting on K/S of printed nano-form:

TABLE 4: COMPARISON BETWEEN USING PRE-MORDANTING AND SIMULTANEOUS MORDANTING ON K/S OF PRINTED ORIGINAL-FORM

| Nature of fabric | Dye conc. % | K/S of samples without mordant | K/S of samples with Alum mordant | | K/S of samples with Tannic Acid mordant | |
|------------------|-------------|--------------------------------|----------------------------------|------|---|------|
| | | | I | II | I | II |
| Wool | 3% | 1.49 | 1.63 | 1.32 | 2.32 | 2.09 |
| | 5% | 2.18 | 2.46 | 1.71 | 3.45 | 2.39 |
| | 7% | 2.24 | 2.78 | 2.40 | 3.29 | 2.28 |
| Silk | 3% | 1.31 | 1.11 | 1.20 | 5.16 | 2.27 |
| | 5% | 2.06 | 1.92 | 1.45 | 6.89 | 2.71 |
| | 7% | 2.17 | 1.95 | 1.94 | 5.54 | 3.17 |

| | | | | | | |
|--------|----|------|------|------|------|------|
| Cotton | 3% | 0.51 | 0.47 | 0.62 | 1.31 | 1.43 |
| | 5% | 1.50 | 1.48 | 0.95 | 2.18 | 2.15 |
| | 7% | 1.48 | 1.58 | 1.66 | 2.81 | 2.23 |

(I): K/S of the mordant was applied via padding technique.

(II): K/S of the mordant was incorporated direct in the printing paste.

TABLE 5: COMPARISON BETWEEN USING PRE-MORDANTING AND SIMULTANEOUS MORDANTING ON K/S OF PRINTED NANO-FORM.

| Nature of fabric | Dye conc. % | K/S of samples without mordant | K/S of samples with Alum mordant | | K/S of samples with Tannic Acid mordant | |
|------------------|-------------|--------------------------------|----------------------------------|------|---|------|
| | | | I | II | I | II |
| Wool | 3% | 2.47 | 3.54 | 2.06 | 3.83 | 2.53 |
| | 5% | 2.72 | 3.45 | 2.56 | 3.91 | 3.29 |
| | 7% | 2.75 | 3.26 | 2.25 | 3.85 | 2.73 |
| Silk | 3% | 2.53 | 1.95 | 1.80 | 6.82 | 2.47 |
| | 5% | 2.73 | 2.46 | 2.55 | 7.39 | 3.75 |
| | 7% | 2.21 | 2.00 | 2.03 | 6.41 | 3.06 |
| Cotton | 3% | 1.73 | 1.37 | 1.17 | 2.53 | 1.61 |
| | 5% | 3.34 | 3.20 | 1.96 | 3.43 | 3.02 |
| | 7% | 1.81 | 2.12 | 1.63 | 3.00 | 2.24 |

(I): K/S of the mordant was applied via padding technique.

(II): K/S of the mordant was incorporated direct in the printing paste

It's clear from the data of **Table 5** on using Alum mordant: K/S values of the pre-mordanting acquired the higher values than the simultaneous mordanting on wool and cotton fabrics. On using tannic acid mordant: K/S values of the pre-mordanting acquired the higher values than the simultaneous mordanting irrespective of the fabric used or curcuma concentrations.

3.2.7. Effect of miniaturization on fastness properties of curcuma printed samples: The

color fastness properties of the natural fabrics printed with curcuma in presences of different mordants (Alum or Tannic acid) or without mordant were measured.

Table 6 represents the data for the K/S values and the color fastness to washing, to rubbing, and to perspiration for deferent fabrics (Wool-Silk - Cotton) printed with curcuma before and after miniaturization.

TABLE 6: COLOR STRENGTH (K/S) AND OVERALL FASTNESS PROPERTIES OF WOOL, SILK AND COTTON PRINTED WITH CURCUMA BEFORE AND AFTER MINIATURIZATION.

On wool:

| Printed fabric | a) Before miniaturization: Samples before miniaturization | | | Washing fastness | | Rubbing fastness | | Perspiration | | | |
|----------------|---|--|-----------------------|------------------|-----|------------------|-----|--------------|-----|----------|-----|
| | Mordant | Dye conc. gm / 100 ml H ₂ O | K/S of Printed fabric | Alt. | St. | Dry | Wet | Acidic | | Alkaline | |
| | | | | | | | | Alt. | St. | Alt. | St. |
| Wool | Without Mordant | 3 | 1.49 | 4-5 | 4 | 4-5 | 4-5 | 3 | 2-3 | 3 | 3 |
| | | 5 | 2.18 | 4-5 | 4 | 4 | 4 | 3 | 2-3 | 3-4 | 3 |
| | | 7 | 2.24 | 4-5 | 4 | 4 | 4 | 3 | 3 | 3-4 | 3-4 |
| | With Alum mordant | 3 | 1.63 | 4-5 | 4-5 | 4 | 4 | 3-4 | 3-4 | 3-4 | 3-4 |
| | | 5 | 2.46 | 4-5 | 4-5 | 4 | 3-4 | 3-4 | 3 | 4 | 3-4 |
| | | 7 | 2.78 | 4-5 | 4 | 4 | 3-4 | 3-4 | 3 | 4 | 4 |
| | With Tannic acid | 3 | 2.01 | 4-5 | 4 | 4-5 | 4-5 | 3-4 | 3 | 3-4 | 3 |
| | | 5 | 2.32 | 4-5 | 4 | 4-5 | 4 | 2-3 | 2-3 | 3 | 2-3 |
| | | 7 | 3.45 | 4-5 | 4 | 4-5 | 3-4 | 3 | 2-3 | 3-4 | 3 |

Alt. : Alteration St.: Staining

b) After miniaturization

| Printed fabric | Samples After miniaturization | | | Washing fastness | | Rubbing fastness | | Perspiration | | | |
|----------------|-------------------------------|--|-----------------------|------------------|-----|------------------|-----|--------------|-----|----------|-----|
| | Mordant | Dye conc. gm / 100 ml H ₂ O | K/S of Printed fabric | Alt. | St. | Dry | Wet | Acidic | | Alkaline | |
| | | | | | | | | Alt. | St. | Alt. | St. |
| Wool | Without mordant | 3 | 2.47 | 4-5 | 4 | 4 | 4 | 3-4 | 3 | 3-4 | 3-4 |
| | | 5 | 2.72 | 4-5 | 4 | 4-5 | 4-5 | 3-4 | 3-4 | 3-4 | 3-4 |
| | | 7 | 2.75 | 4-5 | 4 | 4-5 | 4 | 3-4 | 3 | 3-4 | 3-4 |
| | With Alum | 3 | 3.54 | 4-5 | 4-5 | 4 | 3-4 | 4 | 3-4 | 4 | 4 |
| | | 5 | 3.45 | 4-5 | 4-5 | 4 | 3 | 4 | 3-4 | 4-5 | 4 |
| | | 7 | 3.26 | 4-5 | 4 | 4 | 3-4 | 4 | 4 | 4-5 | 4 |
| | With Tannic acid | 3 | 3.83 | 4-5 | 4 | 4-5 | 3-4 | 3-4 | 3-4 | 3-4 | 3 |
| | | 5 | 3.91 | 4-5 | 4 | 4-5 | 3-4 | 3-4 | 3-4 | 3-4 | 3 |
| | | 7 | 3.85 | 4-5 | 4 | 4 | 4 | 3-4 | 3-4 | 3-4 | 3 |

Alt.: Alteration St.: Staining

On Silk:

a) Before miniaturization:

| Printed fabric | Samples before miniaturization | | | Washing fastness | | Rubbing fastness | | Perspiration | | | |
|----------------|--------------------------------|--|-----------------------|------------------|-----|------------------|-----|--------------|-----|----------|-----|
| | Mordant | Dye conc. gm / 100 ml H ₂ O | K/S of Printed fabric | Alt. | St. | Dry | Wet | Acidic | | Alkaline | |
| | | | | | | | | Alt. | St. | Alt. | St. |
| Silk | Without mordant | 3 | 1.31 | 4-5 | 4 | 4-5 | 4-5 | 4 | 4 | 3 | 3 |
| | | 5 | 2.06 | 4-5 | 4 | 4-5 | 4 | 4 | 3-4 | 3 | 3 |
| | | 7 | 2.17 | 4-5 | 4 | 4-5 | 3-4 | 4 | 3-4 | 3 | 3 |
| | With Alum | 3 | 1.11 | 4-5 | 4-5 | 4 | 4 | 4 | 4 | 4 | 3-4 |
| | | 5 | 1.92 | 4-5 | 4-5 | 4 | 4 | 4 | 3-4 | 4 | 3-4 |
| | | 7 | 1.95 | 4-5 | 4 | 4 | 4 | 4 | 4 | 4 | 4 |
| | With Tannic acid | 3 | 5.16 | 4-5 | 4 | 4 | 4 | 3-4 | 3-4 | 3-4 | 3 |
| | | 5 | 6.89 | 4-5 | 4 | 4 | 2-3 | 4 | 3-4 | 3-4 | 3 |
| | | 7 | 5.54 | 4-5 | 3-4 | 4 | 3 | 4 | 3-4 | 3-4 | 3 |

Alt. : Alteration St.: Staining

b) After miniaturization

| Printed fabric | Samples After miniaturization | | | Washing fastness | | Rubbing fastness | | Perspiration | | | |
|----------------|-------------------------------|--|-----------------------|------------------|-----|------------------|-----|--------------|-----|----------|-----|
| | Mordant | Dye conc. gm / 100 ml H ₂ O | K/S of Printed fabric | Alt. | St. | Dry | Wet | Acidic | | Alkaline | |
| | | | | | | | | Alt. | St. | Alt. | St. |
| Silk | Without mordant | 3 | 2.53 | 4-5 | 4 | 4-5 | 3-4 | 4 | 3-4 | 3-4 | 3 |
| | | 5 | 2,73 | 4-5 | 4 | 4-5 | 3 | 4 | 4 | 3-4 | 3-4 |
| | | 7 | 2.21 | 4-5 | 4 | 4 | 3-4 | 4-5 | 4-5 | 3-4 | 3-4 |
| | With Alum | 3 | 1.95 | 4-5 | 4-5 | 4-5 | 4 | 4-5 | 4 | 4-5 | 4 |
| | | 5 | 2.46 | 4-5 | 4-5 | 4 | 4 | 4-5 | 4-5 | 4-5 | 4-5 |
| | | 7 | 2.00 | 4-5 | 4-5 | 4-5 | 4 | 4-5 | 4-5 | 4-5 | 4-5 |

| | | | | | | | | | | |
|------------------|---|------|-----|---|-----|-----|---|-----|-----|-----|
| With Tannic acid | 3 | 6.82 | 4-5 | 4 | 4 | 3-4 | 4 | 3-4 | 3-4 | 3-4 |
| | 5 | 7.93 | 4-5 | 4 | 4 | 2-3 | 4 | 3-4 | 3-4 | 3-4 |
| | 7 | 6.41 | 4-5 | 4 | 3-4 | 2-3 | 4 | 4 | 3-4 | 3-4 |

Alt.: Alteration St.: Staining

On cotton:

| a) Before miniaturization: | | | | Washing fastness | | Rubbing fastness | | Perspiration | | | |
|----------------------------|------------------|--|-----------------------|------------------|-----|------------------|-----|--------------|-----|----------|-----|
| Printed fabric | Mordant | Dye conc. gm / 100 ml H ₂ O | K/S of Printed fabric | | | | | Acidic | | Alkaline | |
| | | | | Alt. | St. | Dry | Wet | Alt. | St. | Alt. | St. |
| Cotton | Without mordant | 3 | 0.51 | 4-5 | 4 | 4-5 | 4 | 3-4 | 3-4 | 3-4 | 3-4 |
| | | 5 | 1.50 | 4-5 | 4 | 4-5 | 3 | 3-4 | 3-4 | 3-4 | 3-4 |
| | | 7 | 1.48 | 4-5 | 4 | 4-5 | 3 | 3-4 | 3 | 3-4 | 3-4 |
| | With Alum | 3 | 0.47 | 4-5 | 4-5 | 4-5 | 4-5 | 4 | 4 | 4 | 4 |
| | | 5 | 1.48 | 4-5 | 4-5 | 4-5 | 4 | 4 | 4 | 4 | 4 |
| | | 7 | 1.58 | 4-5 | 4-5 | 4-5 | 4 | 4 | 3-4 | 4 | 3-4 |
| | With Tannic acid | 3 | 1.31 | 4-5 | 4-5 | 4-5 | 4-5 | 3-4 | 3-4 | 3-4 | 3 |
| | | 5 | 2.18 | 4-5 | 4 | 4-5 | 4 | 3-4 | 3-4 | 3-4 | 3 |
| | | 7 | 2.81 | 4-5 | 4 | 4-5 | 4 | 3-4 | 3-4 | 3-4 | 3-4 |

Alt. : Alteration St.: Staining

| b) After miniaturization | | | | Washing fastness | | Rubbing fastness | | Perspiration | | | |
|--------------------------|------------------|--|-----------------------|------------------|-----|------------------|-----|--------------|-----|----------|-----|
| Printed fabric | Mordant | Dye conc. gm / 100 ml H ₂ O | K/S of Printed fabric | | | | | Acidic | | Alkaline | |
| | | | | Alt. | St. | Dry | Wet | Alt. | St. | Alt. | St. |
| Cotton | Without mordant | 3 | 1.73 | 4-5 | 4 | 4-5 | 3-4 | 4 | 4 | 4 | 3-4 |
| | | 5 | 3.34 | 4-5 | 4 | 4-5 | 3-4 | 4 | 4 | 4 | 3-4 |
| | | 7 | 1.81 | 4-5 | 4-5 | 4-5 | 3-4 | 4 | 4 | 4 | 4 |
| | With Alum | 3 | 1.37 | 4-5 | 4-5 | 4-5 | 4 | 4-5 | 4 | 4 | 3-4 |
| | | 5 | 3.20 | 4-5 | 4-5 | 4-5 | 4-5 | 4-5 | 4 | 4-5 | 4 |
| | | 7 | 2.12 | 4-5 | 4-5 | 4-5 | 4 | 4-5 | 4-5 | 4-5 | 4-5 |
| | With Tannic acid | 3 | 2.53 | 4-5 | 4-5 | 4-5 | 4 | 4 | 4 | 4 | 3-4 |
| | | 5 | 3.43 | 4-5 | 4-5 | 4-5 | 3-4 | 4 | 4 | 4 | 3-4 |
| | | 7 | 3.00 | 4-5 | 4-5 | 4-5 | 4 | 4-5 | 4-5 | 4 | 3-4 |

Alt.: Alteration St.: Staining

The first glance at the result of **Table 6** would imply that the color strength (K/S) for the printed samples before the miniaturization is much lower than after miniaturization.

Printability of the nano-dye particles would be governed by several factors of which nature of the substrate to be printed comes to play an important role. For example on wool fabric: before miniaturization: the data shows that washing and

rubbing properties ranging from very good to excellent whereas the perspiration range from good to very good. While after the miniaturization: the overall properties ranging from very good to excellent. With respect to fastness properties, there is a tendency of improvement of the perspiration fastness while keeping the washing and rubbing fastness unaltered after miniaturization of the curcuma dye.

CONCLUSIONS:

- Nanoscale curcuma natural dye with particle size less than 100 nm were successfully prepared by using ultrasonic stirrer.
- Increasing the dye concentration from 3 to 7gm/ 100ml water increases the average of dye particle size from 43.7 nm to 56.1nm with greater tendency of the nanoparticles to aggregate/agglomerate when higher dye concentrations were used.
- In absence of mordant, proteinic fabrics i.e. wool and silk acquire high affinity for natural colors than cellulosic fiber i.e. cotton.
- Irrespective of the fabric used, the K/S values of nano samples are higher than original samples.
- Alum mordant incorporate with original curcuma can be substituted by nano-curcuma.
- The nano curcuma acquired the highest K/S values compared with original curcuma, and nano-curcuma incorporated with nano-tannic acid at dye concentration 5%.
- K/S values of the pre-mordanting acquired the higher values than the simultaneous mordanting irrespective of the fabric used or dye particles size used or curcuma concentrations on using tannic acid mordant.
- Rubbing and perspiration fastness properties of nano-dye is better than original dye.

REFERENCES:

1. Siva R.; "Status of Natural Dyes and Dye-Yielding Plants in India". *Current Sci.*, 2007; 92, pp. 916-925.
2. Yi E., Cho J.; "Color Analysis of Natural Colorant-Dyed Fabrics." *Color Res. & Appl.*, 2008; 23, pp. 148-160.
3. Han S. and Yang Y.; "Antimicrobial activity of wool fabric treated with curcumin, Dyes and Pigments", 2005; 64, pp. 157-160.
4. Bechtold T. and Mussak R.; *Handbook of Natural Colorants*. John Wiley & Sons Ltd, 2009.
5. Mohammad M., Loghman K.; "Antibacterial Dyeing Of Polyamide Using Turmeric as a Natural Dye." *AUTEX Research Journal*, June 2013; 13(2): pp. 51-56.
6. Kokate. C.K., Purohit. A.P., & Gokhale. S.B.; "Test book of Pharmacognosy", 2007; 39th Ed., pp.414-415.
7. Ghoreishian S.M., Maleknia L., Mirzapour H. &Norouzi M.; "Antibacterial properties and color fastness of silk fabric dyed with turmeric extract, *Fibers and Polymers*", 2013; 14(2): pp. 201–207..
8. Gulrajani M.L., Gupta D.; "Natural Dyes and their Application to Textiles". *Indian Institute of Technology, Delhi*, 1992.
9. Bermel A.D. and bugner D.E.; *The Journal of Imaging Science Technology*, 1999; 43, p. 78.
10. Fang K. et. al.; *Coloration Technology*, 2005; 121, p. 325.
11. Patra and Gouda; "Application of nanotechnology in textile engineering: An overview", *J. Eng. Technol. Res.*, 2013; 5(5): pp. 104-111.
12. National Nanotechnology Initiative. What is nanotechnology? Retrieved July 26, 2015, from National Nanotechnology Initiative:<http://www.nano.gov/nanotech-101/what/definition>
13. Qian L., Juan P., Hinezoza; "Application of nano-technology for high performance textiles", *JTATM*, Summer 2004; 4(1): pp. 1-7.
14. Wong Y.W.T., Yuen C.W.M., Leung M.Y.S., Ku S.K.A., & Lam H.L.I.; "Selected Applications on Nano-technology in Textiles.", *AUTEX Research J.*, 2006; 6, PP.1-8.
15. Industry Canada. (2013, July 5) <http://www.ic.gc.ca/eic/site/textiles-textiles.nsf/eng/tx03232.htm> 1
16. <http://www.jeolusa.com/PRODUCTS/Transmission-Electron--Microscopes-TEM/200-kV/JEM-2100Plus> (2016)
17. J. Neves, "Technologia Textil", LLS Edn., Porto, Portugal, 1982; 1.
18. The Society of dyer and colorists; "Standard methods for the Assessment of color fastness of textiles", Third Report of the fastness tests coordinating committee, Yorkshire, England, 1955; 71, p.24.
19. Zh Guo L., Hao W., Yun Y.W., Dingjiu X.; *Forest Research*, Beijing. Chinese Academy of Forestry, Beijing, China, 2002; 15 (4): pp 474 -478..

How to cite this article:

Ragheb AA, Tawfik S, Abd -El Thalouth JI and Mosaad MM: Development of printing natural fabrics with curcuma natural dye via nanotechnology. *Int J Pharm Sci Res* 2017; 8(2): 611-20.doi: 10.13040/IJPSR.0975-8232.8(2).611-20.

All © 2013 are reserved by International Journal of Pharmaceutical Sciences and Research. This Journal licensed under a Creative Commons Attribution-NonCommercial-ShareAlike 3.0 Unported License.

This article can be downloaded to **ANDROID OS** based mobile. Scan QR Code using Code/Bar Scanner from your mobile. (Scanners are available on Google Playstore)