



Received on 29 March, 2018; received in revised form, 25 June, 2018; accepted, 02 July, 2018; published 01 December, 2018

COMPARATIVE STUDY OF LEVOCETIRIZINE ELIMINATION BY PRISTINE AND POTASSIUM PERMANGANATE MODIFIED ACTIVATED CHARCOAL

Jasim Hamadi Hassen^{*1}, Yasir Mohammad Farhan² and Abdalkareem Hamad Ayfan¹

Department of Pharmaceutical Chemistry¹, Department of Clinical Pharmacy², College of Pharmacy, University of Anbar, Ramadi, Iraq.

Keywords:

Levocetirizine,
Activated charcoal, Adsorption,
Potassium permanganate, Elimination

Correspondence to Author:

Jasim Hamadi Hassen

Department of Pharmaceutical
Chemistry, College of Pharmacy,
University of Anbar, Ramadi, Iraq.

E-mail: Jasimhu@hotmail.com

ABSTRACT: The elimination capacity of pristine powder activated charcoal PAC and powder activated charcoal modified with potassium permanganate MPAC to remove levocetirizine drug was investigated. The activated charcoal was impregnated with KMnO_4 100 mg/L in order to improve the surface properties. The influence of concentration, time and pH on the adsorption of levocetirizine drug was conducted by means of UV-Vis spectroscopy. The experiments were carried out using two lines. Line 1; adsorption of the drug on pristine PAC and line 2; adsorption on MPAC. By batch experiments, the effect of levocetirizine concentrations of 25, 50, 75, and 100 mg/L, a reaction time of 15, 30, 45 and 60 min, and pH of 2, 4, 7 and 9 were investigated. The results showed that elimination capacity of both PAC and MPAC increased with increasing the drug concentration and time of contact and decreased with decreasing the pH. The elimination efficiency of MPAC found to be greater than that of PAC.

INTRODUCTION: Activated charcoal is one of the main effective adsorbents which has a high surface area, large pore volume, tunable pore size, chemical stability and high hydrophobicity^{1, 2, 3}. It is in the shape of a fine black odorless, tasteless, microcrystalline powder⁴. Due to its high adsorptive capacity is used as an adsorbent for a large variety of compounds. It is used for removal of colors from solutions^{5, 6}. Activated charcoal is used in the adsorption of gases and vapors such as ammonia, carbon tetrachloride, methane, nitrogen dioxide and carbon dioxide^{7, 8, 9}. A large number of studies concern the adsorption of a variety of organic compounds on activated charcoal have been conducted.

From these studies adsorption of phenol, diethyl phthalate, dibutyl phthalate and many other compounds^{10, 11, 12}. In the pharmaceutical field, activated charcoal has been used as an antidote for the majority of poisons because of its ability to prevent the absorption of many toxic agents and enhance the removal of many absorbed drugs. It is used as an antifatulent, and as a good treatment to reduce blood lipid concentrations in patients having uremia and diabetes¹³, adsorption of odors from wounds¹⁴.

Activated charcoal has been used as an adsorbent for a wide range of different drugs like paracetamol¹⁵, tramadol hydrochloride¹⁶, diazepam¹⁷, acetaminophen¹⁸ and many others. In recent years, many researchers have dedicated to research on modification of activated charcoal to improve the adsorption capacity^{19, 20, 21, 22}. One of the important methods is to oxidize the structure by oxidizing agents^{23, 24}. Oxidization with ozone²⁵, concentrated nitric acid^{26, 27} and hydrogen peroxide²⁸ can enhance the adsorption of functional groups

<p>QUICK RESPONSE CODE</p>	<p>DOI: 10.13040/IJPSR.0975-8232.9(12).5155-60</p> <hr/> <p>Article can be accessed online on: www.ijpsr.com</p> <hr/> <p>DOI link: http://dx.doi.org/10.13040/IJPSR.0975-8232.9(12).5155-60</p>
-----------------------------------	---

of carboxylic acids and some other organic compounds. It was found that oxidizing the structure of activated charcoal change its inert and hydrophobic nature and enhance the wettability for polar solvents²⁹.

Granular activated charcoal modified with potassium permanganate was used to enhance the adsorption capacity for phenol. It was found that modification experiment increases the efficiency of activated charcoal adsorption by 20%³⁰. Modification with potassium permanganate increases the removal efficiency of activated charcoal for removal of Cr(VI)^{31, 32} and Cu²⁺³³ from aqueous solution. The effect of oxidation of the organic matter by potassium permanganate before adsorption on activated charcoal and oxidizing activated charcoal and then adsorbing organic matter was also investigated³⁴. Some researchers have found that permanganate is not adsorbed on the activated charcoal but reduced. The reduction process was found to be strongly pH dependent, and the product of reduction is mainly Mn²⁺. The Mn²⁺ ion adsorbed onto the activated charcoal particles by surface complexation³⁵. A study of adsorption of levofloxacin on granular activated carbon produced from date (*Phoenix dactylifera* L.) stones showed adsorption capacity of 100.3 mg/g³⁶.

The removal of levofloxacin by means of alumina-doped coconut coir charcoal impregnated with alumina nanoparticles showed that the adsorption isotherm data were best represented by both Langmuir and Temkin isotherm³⁷. Activated charcoal produced from sugarcane bagasse removes 37% from levofloxacin drug in 90 min reaction time. The reaction isotherm follows Langmuir model³⁸. The adsorption of levofloxacin drug on goethite has been studied. The study concern the effects of nitrate, sulfate, small organic acids and humic acid on the adsorption process. It was shown that the presence of nitrate or sulfate had no effect, but the presence of humic acid increase the process³⁹. The adsorption of levofloxacin on activated charcoal produced from rice husk was found to be spontaneous and endothermic while the adsorption on activated charcoal produced from a wood chip is spontaneous and exothermic⁴⁰. A waste produced from corn bracts and later modified using

zirconium cations were used for removal levofloxacin drug from waste water. The waste exhibited 73 mg/g adsorption capacity⁴¹. The adsorption of the gliclazide drug on activated charcoal was found to be pH, concentration and time-dependent⁴². The aim of this research is to compare the elimination levels of levocetirizine by pristine and modified activated charcoal and to study the effects of concentration, time and pH on the process.

MATERIALS AND METHODS: The activated charcoal used was obtained from Sigma-Aldrich, after repeatedly washed with distilled water and dried to constant weight at 105 °C for over 3 h. The drug sample of levocetirizine is a production of TDA Pharma. All chemicals used in this work were of analytical grade obtained from Sigma-Aldrich.

The electronic spectra were recorded on PG instruments T80 UV/Vis double beam spectrophotometer. The pH was monitored using a Philips (PW-9409) digital pH meter.

The wavelength at which maximum absorbance occurs (λ_{max}) was recorded for the aqueous solutions of drug and found to be 230 nm.

An exact weight of 50 mg of levocetirizine was dissolved in 250 ml distilled water in a 500 ml volumetric flask. The solution was shaken to dissolve all the drug partials and the volume was adjusted up to the mark of the flask with distilled water to obtain a stock solution of 100 mg/L. The solution was filtered using Whatman filter paper no. 41.

Modification Method of Activated Charcoal: Modification of activated charcoal was conducted by immersing the powder in a solution of potassium permanganate 100 mg/L under a neutral condition for 4 h with slow stirring. The mixture then separated and washed repeatedly with distilled water to no color and dried to constant weight at 105 °C for 4 h in order to remove the content of impregnation solvent and water.

Adsorption Studies: Adsorption experiments were performed to study the effects of important parameters such as concentration, time and pH. The experiments were performed on both pristine PAC and MPAC separately.

The flask containing 50 ml of levocetirizine solution of concentrations 25, 50, 75 and 100 mg/L were shaken with 0.5 gm activated charcoal for 1 hour for concentration study.

For time study, 50 ml of drug solution 100 mg/L were shaken with 0.5 gm activated charcoal for 15, 30, 45 and 60 min.

For pH study, 50 ml of drug solution 100 mg/L were shaken with 0.5 gram of activated charcoal for 1 h at pH of 2, 4, 7 and 9. The mixtures were shaken vigorously at room temperature on magnetic stirrer after which filtered through filter paper and the filtrate solutions were analyzed spectrophotometrically at $\lambda = 230$ for residual drug concentration. The process was repeated for PAC and MPAC under different equilibrium conditions of concentration, time and pH. The pH was adjusted using 0.1 N solutions of HCl and NaOH.

The amount of the drug adsorbed was calculated using the equation:

$$Q_e = (C_o - C_e) V / m$$

Where Q_e is the maximum quantity of the drug in mg/gm adsorbed on the activated charcoal, C_o is the initial concentration (mg/L) of the drug solution, C_e is the concentration of the drug (mg/L) in the supernatant at the equilibrium stage, V is the volume of the drug solution in liter and m is the mass of adsorbent employed in grams.

The calibration curve was conducted by measuring the absorbance of solutions for each experiment, then plotting the absorbance versus concentrations, time and pH.

RESULTS AND DISCUSSION: Levocetirizine is a selective H_1 -antihistamine drug used for the treatment of allergic rhinitis and chronic idiopathic urticaria. It is an off-white crystalline powder soluble in water. The chemical formula is $C_{21}H_{25}ClN_2O_3$. It is the *R*-enantiomer of racemic cetirizine. The chemical name of the drug is 2-[2-[4-[(*R*)-(4-chlorophenyl)-phenyl methyl] piperazinyl-1-yl]ethoxy] acetic acid^{43, 44}.

The chemical structure of the drug is shown in **Fig. 1**. The UV spectrum of the levocetirizine solution is shown in **Fig. 2**.

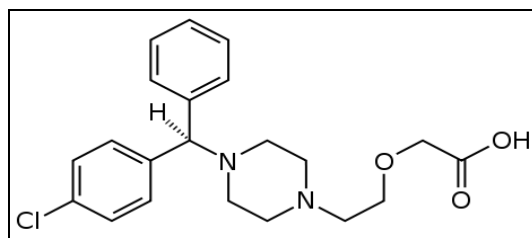


FIG. 1: THE CHEMICAL STRUCTURE OF LEVOCETIRIZINE

The results of concentration for both PAC and MPAC study are listed in **Table 1**.

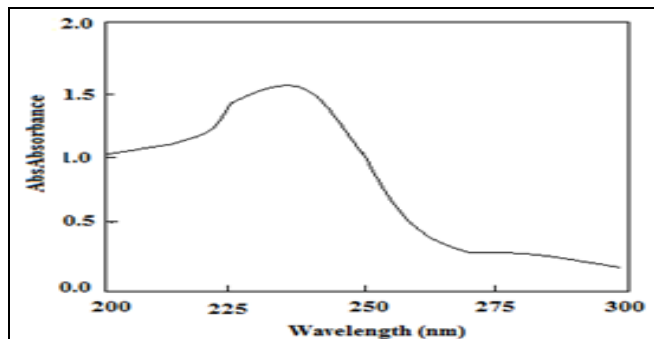


FIG. 2: THE UV SPECTRUM OF LEVOCETIRIZINE

TABLE 1: PARAMETERS OF CONCENTRATION STUDY

Concentration (mg/L)	Levocetirizine Adsorbed on PAC (mg/g)	Levocetirizine Adsorbed on MPAC (mg/g)
25	1.1	1.8
50	2.2	2.8
75	3.2	3.8
100	4.7	4.9

To simulate the adsorption process in the environment of the gastric fluid a sample was used with its additives.

It is clear from **Table 1** that the amounts of the adsorbed drug in mg for each gm of both PAC and MPAC increases almost steadily with increased concentration of the drug solution. At the same time, it seems clear that MPAC adsorbs larger amounts than PAC. The amounts of 4.7 and 4.9 mg of the levocetirizine adsorbed on 1 gm PAC and MPAC respectively in the 100 mg/L concentration seem reasonable.

Fig. 3 is a plot of the amounts of the drug adsorbed on activated charcoal in mg/gm versus concentration for concentration study. The steady increment in the amount of the levocetirizine drug adsorption on PAC and MPAC is very obvious from the plot.

The parameters for time study are listed in **Table 2**. When the time duration of the reaction was changed from 15, 30, 45 to 60 min, the amounts of the drug adsorbed increased with increasing the time for both PAC and MPAC. This time incensement gives the indication that the time of contact is also an important factor for the elimination of the drug. Again the adsorption rate of MPAC was greater that of PAC. The enhancement of adsorption when MPAC is used is very obvious. The relationship between time and the amounts of the adsorbed drug is shown in **Fig 4**. The steady increscent of the adsorption with increasing time is clear.

TABLE 2: PARAMETERS OF TIME STUDY

Time (min)	Levocetirizine Adsorbed on PAC (mg/gm)	Levocetirizine Adsorbed on MPAC (mg/gm)
15	3	4
30	3.2	4.3
45	3.9	5
60	4.2	5.4

Table 3 contains the parameters for pH study. The amounts of the levocetirizine in mg adsorbed on 1gm activated charcoal increasing as the pH of the solution decreased. The highest values of 5.4 and 6.6 mg/gm for the PAC and MPAC respectively found at pH 2, which seems a good result since the pH of the gastric fluid in this rang. The relationship between the pH and the amounts of the adsorbed drug gave a straight line as shown in **Fig 5**. Only

the value at pH 7 for the PAC showed deviation from the straight line.

TABLE 3: PARAMETERS OF pH STUDY

pH	Levocetirizine Adsorbed on PAC (mg/gm)	Levocetirizine Adsorbed on MPAC (mg/gm)
2	5.4	6.6
4	4.3	5.8
7	4	4.5
9	2.5	3.3

From the parameters of the three factors, it is quite clear that the elimination of the levocetirizine drug from the solutions depends on concentration, time and pH. Modification of the activated charcoal by potassium permanganate enhance its elimination capacity in all the experiments factors used.

The enhancement capacity reaches 63% for the 25% concentration as is evident from **Table 4**. A quick glance at the table reveals that the MPAC adsorption capacity was enhanced by about 30% in general.

TABLE 4: % OF ADSORPTION CAPACITY ENHANCEMENT IN MPAC

% Adsorption Enhancement in concentration study	25	50	75	100
	63%	27%	18%	4%
% Adsorption Enhancement in Time Study	15	30	45	60
	33%	34%	28%	28%
% Adsorption Enhancement in pH Study	2	4	7	9
	22%	34%	12%	32%

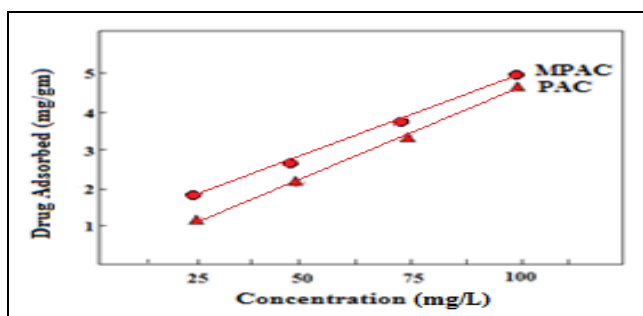


FIG. 3: PLOT OF ADSORBED DRUG (mg/gm) VERSUS CONCENTRATION FOR CONCENTRATION STUDY

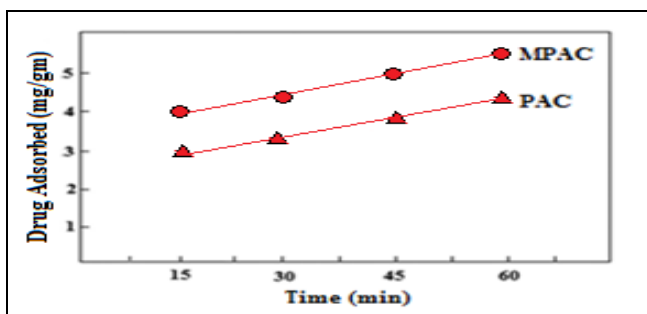


FIG. 4: PLOT OF ADSORBED DRUG (mg/g) VERSUS TIME FOR TIME STUDY

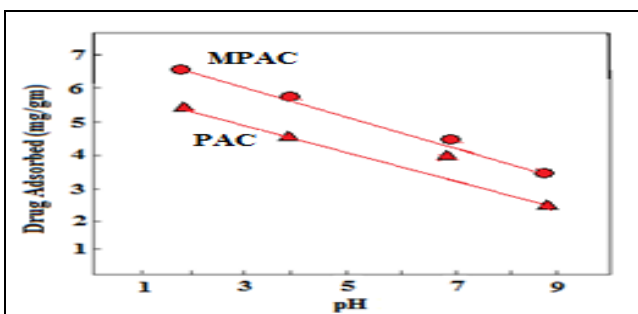


FIG. 5: PLOT OF ADSORBED DRUG (mg/g) VERSUS pH FOR pH STUDY

CONCLUSION: As a comparative investigation, powder activated charcoal PAC and powder activated charcoal impregnated with potassium permanganate MPAC were used to eliminate the levocetirizine drug from solutions. The process include different concentrations (25, 50, 75 and 100 mg/L), different times (15, 30, 45, and 60 min) and different pH (2, 4, 7, and 9). It was found that the elimination rate depends on the concentration, time and pH. The greater the concentration and time the greater the elimination capacity, and the lower the pH the greater the elimination capacity. The enhancement in elimination capacity of MPAC by about 30% was evident in all the variable factors of the experiments.

ACKNOWLEDGEMENT: Authors acknowledge Department of Pharmaceutical Chemistry and the Department of Clinical Pharmacy, College of Pharmacy, University of Anbar, Iraq for providing facilities to carry out this research.

CONFLICT OF INTEREST: The authors do not have any conflict of interest.

REFERENCES:

- Jain A, Balasubramanian R and Srinivasan MP: Hydrothermal conversion of biomass waste to activated carbon with high porosity: A review. *Chemical Engineering Journal* 2016; 283: 789-805.
- Abioye AM and Ani FN: Recent development in the production of activated carbon electrodes from agricultural waste biomass for supercapacitors: A review. *Renewable and Sustainable Energy Reviews* 2015; 52: 1282-1293.
- Hassen JH: Effect of KOH ratio on the formation of activated carbon from pressed wood residues. *International Journal of Pharmaceutical Science and Research* 2017; 8(11): 4875-4880.
- Smisek M and Cerney S: *Active Carbon Manufacture, Properties and Applications*. Elsevier Publishing Company, First Edition 1970.
- Naeem MS, Javed S, Baheti V, Wiener J, Javed MU, Ul Hassen SZ, Mazari A and Naeem J: Adsorption kinetics of acid red on activated carbon web prepared from acrylic fibrous waste. *Fibers and polymers* 2018; 19(1): 71-81.
- Gegel U, Ozcan G and Gurpinar GC: Removal of methylene blue from aqueous solution by activated carbon prepared from pea shells (*Pisum sativum*). *Journal of Chemistry* 2013; 201: 1-9.
- Khan G, Uddin F, Khan MN and Tahir H: Manometrical studies on the adsorption of some organic gases/vapors on the surface of activated charcoal. *The Arabian Journal for Science and Engineering* 2003; 28: 35-41.
- Belhachemi M, Jeguirim M, Limousy L and Addoun F: Comparison of NO₂ removal using date pits activated carbon and modified commercialized activated carbon via different preparation methods: effect of porosity and surface chemistry. *Chemical Engineering Journal* 2014; 253: 121-129.
- Lei H, Wei Y, Zhu L, Yan D, Yadavalli G, Zhang X and Liu Y: Carbon dioxide capture using ammonium sulfate surface modified activated biomass carbon. *Biomass and Bioenergy* 2017; 98: 53-60.
- Bhatnagar A and Sillanpaa M: Removal of natural organic matter (NOM) and its constituents from water by adsorption - A review. *Chemosphere* 2017; 166: 497-510.
- Bouhamidi Y, Kaouah F, Nouri L, Boumaza S and Trari M: Adsorption of diethyl and dibutyl phthalates onto activated carbon produced from *Albixia julibrissin* pods: kinetics and isotherms. *International Journal of Environmental Science and Technology* 2017; 14(2): 271-284.
- Achari VS, Jayasree S and Rajalakshmi AS: Adsorption of p-nitrophenol on coconut shell granular activated carbon: Isotherms, kinetics and thermodynamics. *Indian Journal of Chemical Technology* 2017; 24: 471-478.
- Lapus RM: Activated charcoal for pediatric poisonings: the universal antidote? *Current Opinion in Pediatrics* 2007; 19(2): 216-222.
- Shreve RN, Brink JA and Jr B: *Chemical Process Industries*. McGraw-Hill Books, Fourth Edition 1976.
- Bernal V, Erto A, Giraldo L and Moreno-Piraján JC: Effect of solution pH on the adsorption of paracetamol on chemically modified activated carbons. *Molecules* 2017; 22(7): 1032-1045.
- Pandeya S, Gharti KP, Bharati L and Pandey A: *In-vitro* kinetics, adsorption isotherm, and effect of pH on antidotal effect of activated charcoal in tramadol hydrochloride intoxication. *International Journal of Pharma Sciences and Research* 2016; 7(2): 63-71
- Sah SK, Joshi D, Pathak S, Regmi S, Regmi BM, Manandhar PN, Pandeya S and Marasini N: Effect of ethanol and pH on the *in-vitro* adsorption of diazepam onto activated charcoal from simulated gastric fluid and simulated intestinal fluid. *Indian Journal of Pharmaceutical Science* 2016; 78(5): 624-630.
- Green R, Grierson R, Sitar DS and Tenenbein M: How long after drug ingestion is activated charcoal still effective? *Journal of toxicology. Clinical toxicology* 2001; 39: 601-605.
- Lyubchik SB, Benoit R and Beguin F: Influence of chemical modification of anthracite on the porosity of the resulting activated carbons. *Carbon* 2002; 40(8): 1287-1294.
- Li BZ, Lei ZP, Zhang XH and Huang ZG: Adsorption of simple aromatics from aqueous solutions on modified activated carbon fibers. *Catalysis Today* 2010; 158(3): 515-520.
- Jung MJ, Jeong E, Lim JW, Lee SI and Lee YS: Physico-chemical surface modification of activated carbon by oxyfluorination and its electrochemical characterization. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 2011; 389(1): 274- 280.
- Utrilla JR, Polo MS, Serrano VG, Alvarez PM, Alvim-Ferraz MC and Dias JM: Activated carbon modifications to enhance its water treatment applications. An overview. *Journal of Hazardous Materials* 2011; 187(1): 1-23.
- Jaramillo J, Serrano VG and Alvarez PM: Enhanced adsorption of metal ions onto functionalized granular ACs prepared from cherry stones. *Journal of Hazardous Materials* 2009; 161(2-3): 670-676.
- Cataldo F: Ozone reaction with carbon nanostructures 2: The reaction of ozone with milled graphite and different carbon black grades. *Journal of Nanoscience and Nanotechnology* 2007; 7(4-5): 1446-1454.

25. Jaramilloa J, Lvareza PMA and Serrano VGM: Preparation and ozone-surface modification of activated carbon. Thermal stability of oxygen surface groups. Applied Surface Science 2010; 256(17): 5232- 5236.
26. Stavropoulos GG, Samaras P and Sakellaropoulos GP: Effects of activated carbon modification on porosity, surface structure and phenol adsorption. Journal of Hazardous Materials 2008; 151(2-3): 414-421.
27. Song X, Liu H, Cheng L and Qu Y: Surface modification of coconut-based activated carbon by liquid phase oxidation and its effects on lead ion adsorption. Desalination 2010; 255(1): 78-83.
28. Gomez-Serrano V, Acedo-Ramos M, Lopez-Peinado AJ and Valenzuela-Calahorro C: Oxidation of activated carbon by hydrogen peroxide. Study of surface functional groups by FT-i.r. Fuel 1994; 73(3): 387-395.
29. Wu ZX, Webley PA and Zhao DY: Comprehensive study of pore evolution, mesostructural stability, and simultaneous surface functionalization of ordered mesoporous carbon (FDU-15) by wet oxidation as a promising adsorbent. Langmuir 2010; 26(12): 10277-10286.
30. Zhang J: Phenol removal from water with potassium permanganate modified granular activated carbon. Journal of Environmental Protection 2013, 4: 411-417.
31. Pang M, Liu B, Kano N and Imaizumi H: Adsorption of chromium (VI) onto activated carbon modified with KMnO₄. Journal of Chemistry and Chemical Engineering 2015; 9: 280-287.
32. Deng ZL, Liang MN, Li HH and Zhu ZJ: Advances in preparation of modified activated carbon and its applications in the removal of chromium (VI) from aqueous solutions. International Conference on Water Resource and Environment 2016; 39: 636-642.
33. Yang H, Zhao M, Yang JG, Chai X and Xu Y: Experimental study on the modification of granular activated carbon by potassium permanganate to adsorb Cu²⁺ in the water. Advanced Materials Research 2014; 955-959: 2453-2457.
34. Zhang Y, Wang Y and Zhou L: Influence of excess KMnO₄ on the adsorption of powdered activated carbon. Chemical Engineering Journal 2013; 226: 279-285.
35. Zhang K, Li C, He J and Liu R: Adsorption of permanganate onto activated carbon particles. Journal of West China University of Medical Sciences 1997; 28(3): 344-350.
36. Darweesh TM and Ahmed MJ: Batch and fixed bed adsorption of levofloxacin on granular activated carbon from date (*Phoenix dactylifera* L.) stones by KOH chemical activation. Environmental Toxicology and Pharmacology 2017; 50: 159-166.
37. Limbikai SS, Deshpande NA, Kulkarni RM, Khan AAP and Khan A: Kinetics and adsorption studies on the removal of levofloxacin using coconut coir charcoal impregnated with Al₂O₃ nanoparticles. Desalination and Water Treatment 2016; 57(50): 23918-23926.
38. Khan MA, Saeed K, Abdullah, Ahmad W, Mabood F and Maqsood-ur-Rehman: *In-vitro* adsorption of drugs using modified sugarcane bagasse. Journal of Scientific and Industrial Research 2011; 71: 161-167.
39. Xiaopeng Q, Fei L, Long Z, Hong H, Guangcai W, Fasheng L, and Liping W: Adsorption of levofloxacin to goethite: Batch and column studies. Environmental Engineering Science 2016; 33(4): 235-241.
40. Yi S, Gao B, Sun Y, Wu J, Shi X, Wu B and Hu X: Removal of levofloxacin from aqueous solution using rice-husk and wood-chip biochars. Chemosphere 2016; 150: 694-701.
41. Yu Y, Wang W, Shi J, Zhu S and Yan Y: Enhanced levofloxacin removal from water using zirconium (IV) loaded corn bracts. Environmental Science and Pollution Research 2017; 24(11): 10685-10694.
42. Hassen JH, Ayfan AH and Farhan YM: Spectroscopic evaluation of activated charcoal as a poison antidote for gliclazide drug. Asian Journal of Pharmaceutical and Clinical Research 2018; 11(3): 140-143.
43. Nancy JT and Satish AP: Development and validation of absorbance correction method for simultaneous determination of levocetirizine and ambroxolin in combined tablet dosage form. International Research Journal of Pharmacy 2015; 6(3): 223-226.
44. Choudhari V, Kale A, Abnawe S, Kuchekar B, Gawli V and Patil N: Simultaneous determination of montelukast sodium and levocetirizine dihydrochloride in pharmaceutical preparations by ratio derivative spectroscopy. International Journal of PharmTech Research 2010; 2(1): 4-9.

How to cite this article:

Hassen JH, Farhan YM and Ayfan AH: Comparative study of levocetirizine elimination by pristine and potassium permanganate modified activated charcoal. Int J Pharm Sci & Res 2018; 9(12): 5155-60. doi: 10.13040/IJPSR.0975-8232.9(12).5155-60.

All © 2013 are reserved by International Journal of Pharmaceutical Sciences and Research. This Journal licensed under a Creative Commons Attribution-NonCommercial-ShareAlike 3.0 Unported License.

This article can be downloaded to **ANDROID OS** based mobile. Scan QR Code using Code/Bar Scanner from your mobile. (Scanners are available on Google Playstore)